


## TOPAS<sup>®</sup> 8007F-04

Cyclic Olefin Copolymer

### Processing Conditions for Extrusion

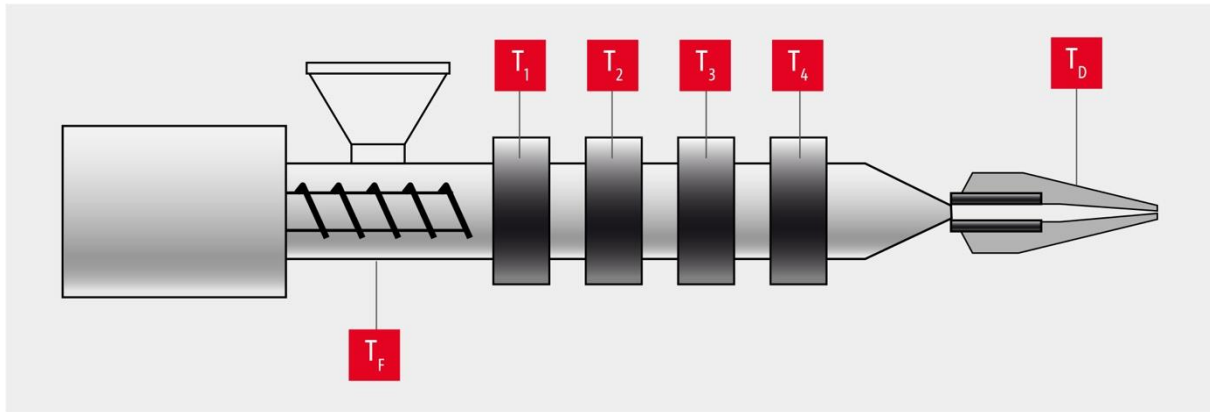

#### Processing Temperatures

$T_F$	$T_1$	$T_2$	$T_3$	$T_4$	$T_D$
20-60 °C *	210-220 °C	230-240 °C	230-240 °C	230-240 °C	230-240 °C
68-140 °F *	410-428 °F	446-464 °F	446-464 °F	446-464 °F	446-464 °F

\* for grooved feed zones:  $T_F$ : approx. 120°C / 248°F

Head Pressure	$P_{melt} > 140 \text{ bar} / 2000 \text{ psi}$ Fine screen packs as needed
Screw Speed	$n_{screw} > 50\% \text{ nominal}$
Screw Design	Multi-purpose or barrier screw w/ mixing section Screw diameter $> 60 \text{ mm} / 2.5 \text{ inch}$ Preferred L/D ratio $\geq 28:1$ where available

#### Note

This grade of TOPAS is the preferred 8007-series product for cast films, and can be extruded on a variety of commercial cast and blown film lines. These recommendations are suggested start-up conditions and must be optimized on the specific extrusion line. Please contact us for further process recommendations.

**IMPORTANT:** This publication contains general advice for processing of our products. It indicates typical processing conditions, and is not intended to cover individual cases. The properties of our products may change as a result of processing conditions or the inclusion of additives. The information contained in this publication should not be construed as a promise or guarantee of specific properties of our products. We strongly recommend that users seek and adhere to the manufacturer's current instructions for handling each material they use, and to entrust the handling of such material to adequately trained personnel only. Please refer to the appropriate Safety Data Sheets before attempting to process our products.

TOPAS Advanced Polymers GmbH | Paulstrasse 3 | 65929 Frankfurt am Main | Germany  
+49 (0) 1805-1-86727 (EU) | +1 859 746-6447 (USA) | +81 3 6711 8615 (Asia/Pacific) | [www.topas.com](http://www.topas.com)